



HAL
open science

Complexions and stoichiometry of the $60.8^\circ//[100](011)$ symmetrical tilt grain boundary in Mg_2SiO_4 forsterite: a combined empirical potential and first-principles study

Jean Furstoss, Pierre Hirel, Philippe Carrez, Patrick Cordier

► To cite this version:

Jean Furstoss, Pierre Hirel, Philippe Carrez, Patrick Cordier. Complexions and stoichiometry of the $60.8^\circ//[100](011)$ symmetrical tilt grain boundary in Mg_2SiO_4 forsterite: a combined empirical potential and first-principles study. *The American Mineralogist*, 2022, 107 (11), pp.2034-2043. 10.2138/am-2022-8420 . hal-03664126

HAL Id: hal-03664126

<https://hal.univ-lille.fr/hal-03664126v1>

Submitted on 7 Nov 2022

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.



Distributed under a Creative Commons Attribution 4.0 International License

REVISION 1 :

Complexions and stoichiometry of the $60.8^\circ//[100](011)$ symmetrical tilt grain boundary in Mg_2SiO_4 forsterite: a combined empirical potential and first-principles study

Jean Furstoss^a, Pierre Hirel^{*,a}, Philippe Carrez^a, Patrick Cordier^{a,b}

^a*Univ. Lille, CNRS, INRAE, Centrale Lille, UMR 8207 - UMET - Unité Matériaux et Transformations, F-59000 Lille, France*

^b*Institut Universitaire de France, 1 rue Descartes, F-75005 Paris, France*

Abstract

In this work we explore the low energy complexions of the symmetrical tilt grain boundary (GB) $60.8^\circ//[100](011)$ in forsterite through molecular dynamics and first principles calculations. Using conservative sampling, we find six stoichiometric complexions with energies ranging from 0.66 to 1.25 J.m^{-2} . We investigate the segregation of MgO vacancy pairs, and find that in most cases it is more favorable for vacancies to lie within the GBs than in the surrounding crystals, leading to new atomic structures. From these results we infer that at finite temperature when vacancies are present in the system, GBs are likely to absorb them and to be non-stoichiometric. We find many GB complexions containing a free oxygen ion, which may have profound implications for geological processes.

word count : 5100 words

1. Introduction

Grain boundaries (GBs) play a key role in numerous physical processes associated with mechanical, chemical diffusion or electrical conductivity behavior of polycrystalline materials (Balluffi and Sutton, 1996). Understanding their properties is therefore particularly important for a mineral like olivine which is the principal constituent of the rocks of the Earth's upper mantle. GBs are involved in several first order processes such as creep (Hirth and Kohlstedt, 1995; Maruyama and Hiraga, 2017a,b), grain boundary migration (Bollinger et al., 2019; Furstoss et al., 2021) or diffusion (Demouchy, 2010; Fei et al., 2016). At the mesoscopic scale, GBs are often viewed as interfaces with particular effective properties, like their mobility or their diffusion coefficient. Unfortunately, their structure at the atomic level is challenging to characterize. At the moment, atomically resolved observations of GB in olivine are scarce as noticed in a recent review by

*Corresponding author: pierre.hirel@univ-lille.fr
Preprint submitted to American Mineralogist

March 21, 2022

11 Marquardt and Faul (Marquardt and Faul, 2018), and the few HRTEM micrographs available in literature
12 Fei et al. (2016); Heinemann et al. (2005); Marquardt and Faul (2018) do not allow determining the chemical
13 composition of GB, i.e. whether the stoichiometry is preserved or not at the GB.

14 In complementarity to experimental efforts, simulations at the atomic scale can provide insight towards
15 the structure of GBs. Yet even that is challenging, due to the complex crystallography of olivine and the
16 many possible GB configurations to explore. Nonetheless, people have used density functional theory (DFT)
17 (Ghosh and Karki, 2014) or classical molecular dynamics (MD) (Adjaoud et al., 2012; Mantsi et al., 2017)
18 to determine physical properties (energy, excess volume) of some select GBs in olivine. Ultimately, the
19 comparison of numerical models with high-resolution observations will be necessary to assess the relevant
20 GB structures, and infer their physical properties.

21 Description of a GB can be done at multiple scales involving different degrees of complexity and precision.
22 At the mesoscopic scale, a GB is generally described by the disorientation between the two adjacent grains,
23 and its energy is almost always described through this variable using extended Read-Shockley type models
24 (initially designed only for low angle GBs) (Gui-Jin and Vitek, 1986; Read and Shockley, 1950). However,
25 a more complete "macroscopic" description should also specify the rotation axis and the crystallographic
26 planes in contact at the GB. At smaller scales, this description can be enriched by indicating the translation
27 vector between the neighboring crystals and finally by describing the atomic arrangement of the GB (e.g.
28 bonds, stoichiometry, charge). Using these lower scale descriptions introduces supplementary degrees of
29 freedom which also impact the physical properties of GB (Han et al., 2016), and question the common
30 assumption that a given disorientation is related to a single GB structure. The multiplicity of GB structures
31 even for a given GB disorientation and contact plane has been considered by several studies essentially for
32 metals (Oh and Vitek, 1986; Rittner and Seidman, 1996) but more rarely for geological relevant materials
33 (Hirel et al., 2019). Recently the concept of GB complexion was introduced (Cantwell et al., 2014) to account
34 for the multiplicity of GB atomic structures. In spite of growing evidence that GBs in a polycrystal may
35 exist in a wide variety of complexions, numerical studies often account only for the complexion of lowest
36 energy, discarding a great number of other possible complexions.

37 In the present work we study the low-energy complexions of a particular GB in the Mg-rich end member of
38 olivine, i.e. forsterite Mg_2SiO_4 , using a combination of molecular statics and ab initio calculations. Forsterite
39 is an orthorhombic crystal in which magnesium ions hold two distinct sites while oxygen ions (three distinct
40 sites) are arranged in tetrahedra with a silicon ion at the center of it. In the following we use the *Pbnm*
41 space group (where the cell parameters are ordered such as $b > c > a$) to describe the forsterite crystal. The

42 studied GB corresponds to a symmetrical tilt grain boundary (STGB) with a disorientation of 60.8° about
43 the [100] direction and (011) planes in contact at GB. This orientation has the particularity to correspond to
44 a high symmetry of the quasi hexagonal close-packed (hcp) oxygen sub-lattice. In fact in such a GB, the hcp
45 stacking of oxygen ions is almost identical to the bulk crystal, which might explain its over-representation
46 in natural olivine aggregates. Indeed, [Marquardt et al. \(2015\)](#) have shown from EBSD measurements on
47 annealed forsterite polycrystals that among GB with 60° disorientation, already highly represented in the
48 misorientation distribution function, the rotation about the [100] axis with a (011) GB plane is the more
49 ubiquitous. Although first principles ([Ghosh and Karki, 2014](#)) and MD ([Adjaoud et al., 2012](#)) works have
50 examined this special STGB, both have focused on a single complexion, which raises the question of its
51 relevance and occurrence in natural systems. Most recent studies of GB in metallic systems have revealed
52 that many metastable configurations are possible and should be accounted for, arguing that materials are
53 rarely in their lowest energy state [Han et al. \(2016, 2017\)](#). In this work, we follow this guideline to come
54 apart from the ground-state GB structure, and explore multiple possible complexions of the GB in forsterite.

55 Here, we first review the low-energy complexions of this STGB by determining their energies, excess
56 volumes and by describing their atomic-scale features. Classical MD simulations allow us to probe the
57 energy landscape and identify low-energy configurations. Then, we perform ab initio calculations in order
58 to characterize more accurately the properties of these configurations.

59 Deviation from stoichiometry at GB has been noticed by several experimental and numerical studies ([Baker](#)
60 [et al., 1990](#); [Farkas, 2000](#)). In fact, GBs are known to be sources and wells of vacancies and therefore it
61 seems interesting to explore the stoichiometry as an other degree of freedom for complexion prospecting
62 by deviating locally from the bulk composition at GB. In ionic compounds such as forsterite, an easy way
63 to deviate from stoichiometry keeping electrically neutral system is to incorporate neutral vacancy pairs.
64 In forsterite, the energetically most favorable Schottky defect is the MgO one ([Brodholt, 1997](#)). Thus we
65 investigate, in a second step, the effect of stoichiometry deviation at GB by inserting MgO vacancy pairs.

66 2. Methodology

67 2.1. Computation techniques

68 Atomistic calculations are performed with LAMMPS ([Plimpton, 1995](#)). Interactions between ions are
69 modelled with a rigid-ion potential accounting for the long-range Coulomb interaction, and short-range
70 interactions are described by a Morse function and a repulsive r^{-12} term. Potential parameters were op-
71 timized by Pedone et al. ([Pedone et al., 2006](#)), where ions have partial charges of $1.2e$, $2.4e$ and $-1.2e$ for

72 Mg, Si and O ions respectively. This allows considering neutral vacancy pairs such as MgO. Moreover this
73 potential was shown to offer a very good description of a number of properties of forsterite including bulk,
74 surfaces and defects properties (Hirel et al., 2021). Coulomb interactions are computed using the particle-
75 particle-particle-mesh (pppm) method (Eastwood et al., 1980). Ion positions are optimized by means of
76 the conjugate-gradients algorithm until the maximum force is smaller than 10^{-10} eV.Å⁻¹. The pressure is
77 maintained at 0 GPa by rescaling the simulation cell.

78 In order to consolidate our results and to investigate possible changes in ionic charge state, we also
79 perform first-principles calculations on some systems containing grain boundaries. We use the Vienna
80 Ab initio Simulation Program (VASP) (Hafner, 2008) with the projector augmented wave (PAW) method
81 (Kresse and Joubert, 1999) in the generalized gradient approximation (GGA) (Perdew et al., 1996). In
82 order to treat explicitly only valence electrons, the interactions between valence, core electrons and nuclei
83 are described by the pseudopotential developed by Perdew and Wang (1992). A cut-off of 500 eV is applied
84 to the plane wave basis and the first Brillouin zone is sampled with Monkhorst-pack grid (Monkhorst and
85 Pack, 1976) using a $2 \times 1 \times 1$ mesh.

86 First-principles calculations give access to the electron density. We perform a Bader analysis, which de-
87 composes the charge density into atomic basins based on a change of sign in the electron density gradient
88 (Bader, 1990). The calculations are performed using the software "Bader Charge Analysis" developed by
89 the Henkelman group (Henkelman et al., 2006; Tang et al., 2009). We use it to quantify the changes in ion
90 charges in GBs with respect to perfect crystal environment.

91 2.2. GB construction

92 We focus on the $60.8^\circ // [100](011)$ symmetric tilt grain boundary (STGB) in forsterite, i.e. where two
93 crystals share a common [100] axis and meet along (011) planes with a disorientation of 60.8° . In forsterite,
94 two different types of (011) planes are possible, with different stoichiometries, as illustrated in Fig. 1. One
95 type of plane is terminated by a silicon ion and the oxygen ions forming the edge of tetrahedra, which we
96 will refer to as edge-planes, and the second type is terminated by Mg ions and an oxygen ion belonging to
97 the tip of a tetrahedron, referred to as tip-planes. We begin by constructing cells of forsterite terminated by
98 the same type of plane (Fig. 1). Such cells preserve the stoichiometry, but must be truncated by $1/2[001]$
99 (which removes one formula unit) to obtain the same type of surface.

100 The GB is constructed by stacking two crystals meeting across (011) planes. In order to avoid any
101 spurious effect due to charged surfaces, we use 3-D periodic boundary conditions (PBC) and ensure that
102 the system remains charge-neutral. Moreover, we also make sure that SiO₄ tetrahedra remain unaffected,

103 because breaking Si-O bonds is energetically unfavorable in this system. Since the GB studied is a STGB,
104 the two crystals are mirror images of each other. Two types of reference GBs are constructed, one by stacking
105 the "edge-plane" system with its mirror image ("edge-to-edge"), and one by stacking the "tip-plane" system
106 with its mirror image ("tip-to-tip").

107 Due to PBC, the same GB is formed at the center of the cell and at the edges (Fig.2). This allows
108 computing the reference GB energy density (γ_{ref} in $\text{J}\cdot\text{m}^{-2}$) and excess volume (V_{ref}^e):

$$\begin{aligned}\gamma_{\text{ref}} &= \frac{E_{\text{tot}} - E_{\text{bulk}}}{2A}, \\ \Omega_{\text{ref}} &= \frac{V_{\text{tot}} - V_{\text{bulk}}}{2A},\end{aligned}\tag{1}$$

109 where E_{tot} and V_{tot} are the total energy and volume of the relaxed system containing the GBs, E_{bulk} and
110 V_{bulk} are the total energy and volume of the equivalent defect free crystal, and A is the area of the GB.

111 We computed the reference GB energy for different system sizes and found that a height of 180 Å is
112 necessary for GB energy and excess volume to be converged, which corresponds to a system containing
113 980 atoms. When performing DFT calculations, we use smaller systems of 420 atoms due to computational
114 costs. Although GB energies are not converged for this system size, our convergence tests show that the
115 atomic structure is the same as in larger systems.

116 2.3. Conservative sampling

117 The method described above does not guarantee an optimal atomic GB structure. An important degree
118 of freedom is the relative translation of the two grains, quantified by a vector $\vec{\tau} = (\tau_x, \tau_y, \tau_z)$. In order to
119 explore this degree of freedom, we impose the translation vector (τ_x, τ_y) in the GB plane, and relax ions
120 in the direction normal to the GB to determine the optimal translation τ_z . Computing the GB energy for
121 each translation vector, one obtains a map of the energy density γ along the GB plane. Similar to the
122 classical generalized stacking faults approaches (Mishin and Farkas, 1998; Vitek, 1968), this method allows
123 identifying low-energy configurations of the GB.

124 The use of 3D PBC requires a special attention to the simulation cell construction and the relaxation scheme
125 involved during the relaxation process (Fig.2). Indeed if a crystal is displaced with respect to the other by
126 keeping the same cell, then the GBs at the center and at the edges of the cell will not be equivalent anymore,
127 thus preventing a direct calculation of the interface energy.

128 For this reason, when the top crystal is translated we tilt the box so that the interface at the edges of

129 the cell remains identical, with the energy E_{ref} . For the given relative translation $\vec{\tau}$, the energy and excess
130 volume of the central GB are then:

$$\begin{aligned}\gamma(\vec{\tau}) &= \frac{E_{\text{tot}}(\vec{\tau}) - E_{\text{bulk}}}{A} - \gamma_{\text{ref}}, \\ \Omega(\vec{\tau}) &= \frac{V_{\text{tot}}(\vec{\tau}) - V_{\text{bulk}}}{A} - \Omega_{\text{ref}}.\end{aligned}\quad (2)$$

131 For a given imposed translation vector (τ_x, τ_y) , we relax atom positions along the direction z normal to the
132 GB. To allow for rotational relaxation of tetrahedra, O ions are relaxed in all directions. Within 25 Å in
133 the vicinity of the central GB, all ions are left free to relax (see Fig.2).

134 After the identification of the lowest energy configurations, the selected systems are fully relaxed (no ionic
135 positions fixed) which provides the final GB complexions and allows computing their energies and excess
136 volumes.

137 2.4. Density and excess volume

138 From the atomistic simulation outputs, we can compute the density profile along a direction normal to
139 the GB plane. In practice, the mass of each atom is expanded through Gaussian distributions (with standard
140 deviation of 2 Å) and the density profile $\rho(z)$ is computed from the contribution of all masses contained in
141 a elementary volume (grid size of 0.2 Å). These calculations are performed with Atomsk (Hirel, 2015).

142 The GB excess volumes can be expressed as a function of the density profile along the direction normal
143 to the GB plane. Indeed the density can be related to a infinitesimal change in volume $dV(z)$:

$$dV(z) = \left(\frac{\rho_{\text{uc}}}{\rho(z)} - 1 \right) Adz, \quad (3)$$

144 where ρ_{uc} is the density of a unit cell. The GB excess volume is then computed by integrating dV around
145 the GB in a length F , and dividing by the GB area:

$$\Omega = \int^F \left(\frac{\rho_{\text{uc}}}{\rho(z)} - 1 \right) dz \quad (4)$$

146 We verified that this methodology yields the same values than the ones given by Eqs. 1 and 2 in the case
147 of stoichiometric GB structures. For non-stoichiometric GBs, Eqs. 1 and 2 are no longer valid and Ω is
148 computed using Eq. 4.

149 3. Stoichiometric grain boundary

150 3.1. Reference grain boundaries

151 As explained in the previous section, the first step toward the calculation of the GB energy landscape
152 is the construction of a reference configuration containing two equivalent GBs. After full relaxation, the
153 edge-to-edge GB (labeled E1) has an energy $\gamma_{E1} = 0.9 \text{ J.m}^{-2}$ and an excess volume $\Omega_{E1} = 0.39 \text{ \AA}$. Its
154 atomic configuration is shown in Fig.4a. Atomic displacements after relaxation are small (about 1.15 \AA)
155 and tetrahedra do not rotate with respect to the [100] direction. Computation of the mass density profile
156 shows that the GB is less dense than the surrounding crystals, which is consistent with the positive excess
157 volume.

158 The tip-to-tip GB (labeled T1) has an energy $\gamma_{T1} = 1.22 \text{ J.m}^{-2}$ and an excess volume $\Omega_{T1} = 0.76 \text{ \AA}$.
159 Displacements are also moderate (about 1.5 \AA), but are associated with significant tetrahedra rotation as
160 shown in Fig.4d. This is probably due to strong repulsion of O ions at the tip of tetrahedra.

161 3.2. GB energy landscapes

162 Following the methodology presented in section 2.3 we computed the GB energy landscape for the
163 two types of GB, which are reported in Fig.3. These landscapes are irregular and present abrupt energy
164 variations, as it was already noticed by Adjaoud et al. (2012). Nonetheless, both surfaces exhibit a central
165 symmetry, which is consistent with the symmetries of the (011) plane in forsterite. In addition to the
166 reference GBs E1 and T1, each energy landscape reveals two more low energy basins, labeled E2, E3, T2
167 and T3. By symmetry, equivalent configurations are found, respectively $E2'=E2$, $E3'=E3$, $T2'=T2$ and
168 $T3'=T3$ (see Fig.3).

169 3.3. Stable configurations

170 Each low energy configuration found from the energy landscape sampling is fully relaxed (i.e. without
171 constraint). We obtain six distinct GB complexions with energies ranging between 0.66 and 1.25 J.m^{-2} .
172 Reference GB complexions E1 and T1 were already presented above.

173 The complexion E2 is shown in Fig.4b. Contrary to the reference E1, it shows significant relaxation with
174 tetrahedra sharing an O ion (orange arrow in Fig.4b), which causes an O ion to become free of any bond with
175 a Si ion (blue arrow in Fig.4b). Although the presence of this free O ion seems unfavorable, the interface
176 energy is $\gamma_{E2} = 0.66 \text{ J.m}^{-2}$, significantly lower than the reference E1. This complexion is also more compact
177 as evidenced by the smaller excess volume (i.e. 0.13 \AA) and the density profile.

178 The complexion E3 is shown in Fig.4c. Like E2 it contains joined tetrahedra and free O ions, however
 179 its energy is the highest with a value $\gamma_{E3} = 1.25 \text{ J.m}^{-2}$. This complexion is the least favorable for the
 180 stoichiometric GBs. It is also associated with a large expansion ($\Omega_{E3} = 0.60 \text{ \AA}$).
 181 Concerning the tip-to-tip configurations, the complexion T2 (Fig.4e) also presents joined tetrahedra and
 182 unbound O ions. Its energy $\gamma_{T2} = 1.08 \text{ J.m}^{-2}$ is lower than the reference T1. Finally, the configuration
 183 T3 also contains joined tetrahedra and free O ions. Its energy is the lowest for the tip to tip GB type,
 184 $\gamma_{E3} = 0.95 \text{ J.m}^{-2}$. It is also the most compact of all complexions, with an excess volume $\Omega_{T3} = 0.13 \text{ \AA}$.

GB label	GB energy (J.m^{-2})		Excess volume (\AA)		ΔE (eV)
	MD	DFT	MD	DFT	
E1	0.90	0.94	0.37	0.49	-2.11
E2	0.66	1.02	0.13	0.39	-1.31
E3	1.25	1.39	0.58	0.63	-2.81
T1	1.22	1.54	0.78	0.76	-1.90
T2	1.08	1.39	0.28	0.42	-2.18
T3	0.95	1.38	0.13	0.34	-2.35
(Ghosh and Karki, 2014)		1.15		0.37	unknown
(Adjaoud et al., 2012)	1.30		0.35		unknown

Table 1: Summary of the stoichiometric GB energies and excess volumes for the different GB complexions obtained by MD and DFT. Labels refer to those in Fig.3, ΔE corresponds to the segregation energy of a MgO vacancy pair.

185 In summary, the most favorable complexions are E2 for the edge-to-edge type, and T3 for the tip-to-tip
 186 type. Both are characterized by tetrahedra connected by an O ion and free O ions remaining in the GB. We
 187 also note a positive correlation between GB energy and excess volume: the lower the GB energy, the lower
 188 its volume. This is consistent with previous studies on similar GBs (Adjaoud et al., 2012; Ghosh and Karki,
 189 2014). From the density profiles we estimate the structural width of GBs to be approximately 10 \AA .

190 3.4. *Ab initio calculations*

191 In order to consolidate results obtained with the interatomic potential, we performed first-principles
 192 calculations as presented in section 2.1. Starting from our previous configurations relaxed with the potential,
 193 we perform a full ionic relaxation by means of DFT calculations.

194 Ionic displacements are negligible, so that the GB atomic structures remain the same for all complexions.
 195 The GB energies and excess volumes obtained by DFT are reported alongside those presented previously
 196 in Tab. 1. We obtain very good agreement between the two methods, thus confirming the suitability of
 197 the potential for modeling GBs. The ordering of GB energies is identical in both methods, except for the
 198 complexions E1 and E2. This small discrepancy may be attributed to the small size of simulation volumes

199 involved in the DFT calculations.

200 Using the electron density from our DFT calculations, we performed Bader analysis to evaluate the charges
201 of ions. Fig. 5b shows the distribution of charge of O ions in a perfect bulk environment (blue curve), with a
202 median value about $-1.61e$, which we consider as the reference charge here. Charge analysis of oxygen ions
203 belonging in GBs show that the latter have little effect on this charge distribution. As an example, we show
204 the charges of O ions in the complexion E2 in Fig. 5b (orange curve). Their distribution is slightly wider
205 than in the bulk, but remains within 1% of the reference charge. Two noticeable exceptions are indicated
206 with arrows. The first one (orange S arrow) corresponds to the O ion bonding two tetrahedra, which has a
207 reduced electron charge. Visualization of its isosurface of charge density (Fig. 5a) shows that it is elongated
208 in the direction of the two Si ions, which indicates mixed ionic and covalent bonding. The second exception
209 is the unbound O ion (blue F arrow in Fig. 5), which has a greater charge of about $-1.65e$. Its isosurface
210 is almost spherical, indicating that this ion is free of covalent bonding. Overall, we find that using an
211 interatomic potential with fixed charges is a reasonable approximation for modelling GBs in forsterite.

212 4. Non-stoichiometric GB: MgO vacancy pairs

213 We investigate the effect of stoichiometry by introducing MgO vacancy pairs in the six GBs presented
214 above. We construct atomic systems corresponding to all possible combinations of Mg and O vacancies,
215 which represents about 800 different systems. After relaxation, we obtain several GB complexions that can
216 be compared with the parent GB complexion. Contrary to the stoichiometric case, the interface energy
217 cannot be computed unambiguously, which will be discussed in section 5. For that reason, in this section we
218 focus on the segregation energies of the vacancies, defined as the difference between the energy of a system
219 where a vacancy pair is inside a grain $\Delta E_{\text{ref}}^{N-2}$, and one where it lies inside the GB E_{tot}^{N-2} :

$$\Delta E = E_{\text{tot}}^{N-2} - E_{\text{ref}}^{N-2} \quad (5)$$

220 This quantity indicates if it is more energetically favorable for the vacancy to be in the bulk phase (i.e.
221 $\Delta E > 0$) or within the GB (i.e. $\Delta E < 0$). Since in forsterite, two Mg sites and three O sites are possible in
222 the perfect crystal, E_{ref}^{N-2} can take multiple values. We choose to take the one that minimizes ΔE , so that
223 it vanishes in the bulk.

224 Fig. 6 presents the segregation energy ΔE as function of the location of the MgO vacancy pair for the
225 complexion E1. We can see that it takes negative values everywhere within the GB, which corresponds to

226 the preferential segregation of vacancies at the GB. We conclude that when such vacancies are present in
227 the system, it is energetically favorable for them to be incorporated in the GB rather than inside a grain.
228 Similar results are obtained for all six complexions, and are available in the supplementary material.

229 *4.1. Configurations of lowest energy*

230 For each initial GB complexion, among all the defective configurations investigated, we select the one
231 with the lowest energy. This leads to six final non-stoichiometric GB complexions. These complexions are
232 associated with segregation energies in the order of -2 eV as reported in Tab. 1.

233 Their atomic configurations are presented in Fig. 7. In the reference complexions E1 and T1, the removal
234 of a MgO pair causes one tetrahedron to miss an O ion and to share one with a neighboring tetrahedron.

235 The stoichiometric complexions E2, E3, T2 and T3 already contained connected tetrahedra and free O ions,
236 as presented in section 3.3. One would expect the most favorable configuration to be the one where the free
237 O ion would be removed. We find that this is true only in the complexion T3n, as shown in Fig. 4f. On the
238 contrary, for complexions E2n, E3n and T2n, we find that the most favorable systems are the ones where
239 the free O ions are untouched, and three tetrahedra are connected, as shown in Figs. 4b, 4c and 4e.

240 Although vacancies were introduced in the GBs, we find that it has a negligible impact on the formation
241 volume, as evidenced by the density profiles shown in Fig. 7. As a result, we expect that a simple measure-
242 ment of the density would not allow to discriminate between the different GB complexions. Here again, we
243 estimate the GB structural widths to be approximately 10 \AA .

244 *4.2. Ab initio calculations*

245 As for the stoichiometric complexions presented in the previous section, we perform DFT calculations
246 on the six non-stoichiometric GBs. Starting from the configurations relaxed with the interatomic potential,
247 we perform a full ionic relaxation with DFT. Again, we find that this relaxation does not change the atomic
248 structure of GBs, indicating that the interatomic potential is efficient for determining GB configurations.
249 In particular, DFT confirms the stability of tetrahedra sharing O ions, as well as the excess volumes (see
250 supplementary materials).

251 We apply Bader analysis to the non-stoichiometric GBs. The results are presented for the non-stoichiometric
252 complexion E2 in Fig. 8. As previously, the shape of isosurfaces allows to recognize mixed ionic and covalent
253 Si-O bonds in tetrahedra, as well as free O ions. Where tetrahedra are connected, shared O ions (arrows
254 labeled S) have a decreased charge, while others O ions belonging to those tetrahedra (arrow labeled T)
255 have a greater charge. As before, free O ions (arrows labeled F) have a higher charge.

256 5. Discussion

257 5.1. Comparison with literature

258 To the best of our knowledge, we have identified for the first time six stoichiometric complexions of the
259 $60^\circ//[001](011)$ GB in forsterite, with formation energies ranging from 0.66 to 1.25 J.m^{-2} . For the same GB,
260 [Adjaoud et al. \(2012\)](#) reported an energy of 1.30 J.m^{-2} and an excess volume of 0.35 \AA using an interatomic
261 potential. First-principles calculations ([Ghosh and Karki, 2014](#)) reported an energy of 1.15 J.m^{-2} and an
262 excess volume of 0.37 \AA . We find that our own values are in good agreement with both numerical studies.
263 Both stoichiometric and non-stoichiometric GBs that we modeled exhibit structural widths of approximately
264 10 \AA , a value commonly observed by transmission electron microscopy for GBs in olivine as reviewed by
265 [Marquardt and Faul \(2018\)](#).

266 Experimental determination of GB energies are more scarce. [Duyster and Stöckhert \(2001\)](#) measured GB
267 energies from dihedral angles in an equilibrated coarse-grained natural peridotite. Their values span between
268 1.12 and 1.47 J.m^{-2} which is in good agreement with our results. The values reported by [Cooper and](#)
269 [Kohlstedt \(1982\)](#) are significantly lower, $0.9 \pm 0.35 \text{ J.m}^{-2}$, probably due to the presence of melt at the
270 interfaces in the olivine-basalt system considered.

271 The linking of tetrahedral units and the free O ions at forsterite GBs, as observed in this work, has never been
272 noticed by prior studies. The finding of [Mantisi et al. \(2017\)](#) that the GBs are almost structureless above
273 3 \AA cannot be confirmed here. Even differing in their structures, the complexions presented here exhibit
274 a short range order which can be apprehended looking at figures 4 and 7. Some structural characteristics
275 highlighted by [Ghosh and Karki \(2014\)](#) are retrieved here such as the conservation of Si ions in a tetrahedral
276 environment and modification of Si-O bond lengths. A continuous treatment of this particular GB by [Sun](#)
277 [et al. \(2016\)](#), shows that the O and Si sub-lattices accommodate the main part of the crystal disorientation,
278 which is in good agreement with the structure of the complexions presented here.

279 The combination of first principles and MD calculations has permitted to improve the confidence on the
280 interatomic potential of [Pedone et al. \(2006\)](#) to the study of GBs in forsterite. All stable complexions found
281 with the potential have been confirmed by *ab initio* calculations with good agreement concerning the GB
282 atomic structures, energies and excess volumes. Charge analysis have shown that the use of fixed partial
283 charges (so-called rigid ion potential) is justified. The small deviations from the reference charge also justify
284 the use of the interatomic potential.

285 *5.2. Effect of stoichiometry*

286 The low energy basins in the energy landscapes are separated by high energy barriers. It implies that GBs
287 cannot change complexion conservatively (e.g. E1 → E2) as it would require too much energy. Adsorption
288 of vacancies at the GB may provide a more favourable path towards a change in GB complexion. We have
289 shown that it is more favorable for the vacancy to be within the GB than in the bulk phase. This finding is
290 in good agreement with the expected vacancy sinks behavior of GBs (Uberuaga et al., 2015).

291 As explained above, the intrinsic GB energy cannot be defined unambiguously when it is non-stoichiometric.

292 One must account for the chemical potential μ_{MgO} of the removed ions:

$$\gamma = \frac{E_{\text{tot}}^{N-2} - E_{\text{bulk}}^N + \mu_{\text{MgO}}}{A} - \gamma_{\text{ref}}, \quad (6)$$

293 The chemical potential depends on environmental conditions. One possible choice is to define it as the
294 lattice energy of MgO periclase, which is $\mu_{\text{MgO}} = -16.57$ eV using the same interatomic potential by
295 Pedone. Nevertheless, other approximations can be done considering for instance $\mu_{\text{MgO}} = \mu_{\text{Mg}_2\text{SiO}_4} - \mu_{\text{MgSiO}_3}$
296 (where $\mu_{\text{Mg}_2\text{SiO}_4}$ and μ_{MgSiO_3} are the lattice energies of forsterite and enstatite respectively), which gives
297 $\mu_{\text{MgO}} = -17.00$ eV; or $2\mu_{\text{MgO}} = \mu_{\text{Mg}_2\text{SiO}_4} - \mu_{\text{SiO}_2}$ (where μ_{SiO_2} is the lattice energy of quartz) which
298 gives $\mu_{\text{MgO}} = -16.44$ eV. Using these values, the GB energy of the E3n complexions (which has the lower
299 segregation energy) should range between 1.60 and 1.76 J.m⁻² which is higher than the one of the parent
300 GB (i.e. 1.25 J.m⁻²). More generally, the energies of the non-stoichiometric complexions are higher than
301 the one of the parent GB.

302 A comparable numerical study (Chua et al., 2010) has also noticed that for different GBs in SrTiO₃ the
303 most stable GBs (i.e. with lowest energies) were the stoichiometric ones, which is in contradiction with the
304 non-stoichiometric GBs experimentally observed SrTiO₃ (Kim et al., 2001; McGibbon et al., 1994; Yang
305 et al., 2013).

306 The GB can be viewed as a phase at equilibrium with other phase (e.g. neighboring grains) (Cantwell et al.,
307 2014) and the minimization of the whole system energy does not necessarily lead to minimization of the GB
308 energy itself. Our calculations show that if vacancies are present in the system, they will segregate at GBs
309 even it increases the GB energy. The GB structure and its energy therefore depend on external factors,
310 which emphasizes the lower importance to give on the GB energy to determine stable GB structures.

311 **6. Implications**

312 The atomic structure of GBs is a key input parameter, as all effective physical properties derive from it.
313 For the one disorientation that we studied here (i.e. 60.8°), we expect each GB complexion to have different
314 properties in terms of mobility, diffusion, segregation, and so forth. We want to stress the importance of
315 considering all possible complexions of GBs when performing atomic-scale simulations, instead of focusing
316 on a single particular complexion.

317 Our work also evidences the attractiveness of GBs for vacancies (Tschopp et al., 2012; Uberuaga et al., 2015),
318 highlighting the exchange capacities between crystal and GBs. At finite temperature, these exchanges should
319 be of first importance for the structure of GBs.

320 A remarkable observation from our study is the presence of an anomalous non-silicate oxygen site in
321 some GBs, which may have several implications. First, these free O ions may diffuse easier than the others
322 (which are bound in tetrahedral environment), which could contribute to the high diffusivity of oxygen in
323 GBs compared to bulk (Yurimoto et al., 1992). It may therefore increase the O vacancy concentration in
324 forsterite GBs.

325 Second, the occurrence of such an unbound O ion is likely to have implications on water storage. The
326 same feature is found in the structure of wadsleyite where it has been shown to strongly favor protonation
327 (Jacobsen et al., 2005; Smyth, 1994). Our calculations suggest the possibility of a strong segregation of
328 hydrogen at GBs with a maximum concentration of $1.74 \cdot 10^{-2} \text{ \AA}^{-2}$ on the basis that each unbound O ion
329 is protonated. Assuming spherical grains the contribution of such a mechanism to hydrogen storage should
330 be of the order of 390, 40 and 4 H/ 10^6 Si for grain sizes of 1, 10 and 100 μm , respectively.

331 Finally, some stable GBs can have relatively high free volumes and we can expect these sparsely dense
332 boundaries to be preferential zones for incompatible elements. Further simulations are required to properly
333 assess these hypotheses.

334 **Acknowledgements**

335 This project has received funding from the French government through the Programme Investissement
336 d'Avenir (I-SITE ULNE / ANR-16-IDEX-0004 ULNE) managed by the Agence Nationale de la Recherche,
337 under the project name NuMoGO, and from the European Research Council (ERC) under the European
338 Union's Horizon 2020 research and innovation programme under grant agreement No 787198 – TimeMan.
339 Computational resources have been provided by the DSI at Université de Lille.

340 References

- 341 Adjaoud, O., Marquardt, K., and Jahn, S. (2012) Atomic structures and energies of grain boundaries in Mg₂SiO₄ forsterite
342 from atomistic modeling, *Physics and Chemistry of Minerals*, 39, 749–760.
- 343 Bader, R. (1990) *Atoms in Molecules: A Quantum Theory*.
- 344 Baker, I., Schulson, E., Michael, J., and Pennycook, S. (1990) The effects of both deviation from stoichiometry and boron on
345 grain boundaries in Ni₃Al, *Philosophical Magazine B*, 62, 659–676.
- 346 Balluffi, R. and Sutton, A. (1996) Why should we be interested in the atomic structure of interfaces?, in: *Materials Science*
347 *Forum*, vol. 207, pp. 1–12, Trans Tech Publ.
- 348 Bollinger, C., Nzogang, B. C., Mussi, A., Bouquerel, J., Molodov, D. A., and Cordier, P. (2019) Microstructural evidence for
349 grain boundary migration and dynamic recrystallization in experimentally deformed forsterite aggregates, *Minerals*, 9, 17.
- 350 Brodholt, J. (1997) Ab initio calculations on point defects in forsterite (Mg₂SiO₄) and implications for diffusion and creep,
351 *American Mineralogist*, 82, 1049–1053.
- 352 Cantwell, P. R., Tang, M., Dillon, S. J., Luo, J., Rohrer, G. S., and Harmer, M. P. (2014) Grain boundary complexions, *Acta*
353 *Materialia*, 62, 1–48.
- 354 Chua, A. L.-S., Benedek, N. A., Chen, L., Finnis, M. W., and Sutton, A. P. (2010) A genetic algorithm for predicting the
355 structures of interfaces in multicomponent systems, *Nature materials*, 9, 418–422.
- 356 Cooper, R. and Kohlstedt, D. (1982) Interfacial energies in the olivine basalt system., *Unknown Journal*, pp. 217–228.
- 357 Demouchy, S. (2010) Diffusion of hydrogen in olivine grain boundaries and implications for the survival of water-rich zones in
358 the Earth's mantle, *Earth and Planetary Science Letters*, 295, 305–313.
- 359 Duyster, J. and Stöckhert, B. (2001) Grain boundary energies in olivine derived from natural microstructures, *Contributions*
360 *to Mineralogy and Petrology*, 140, 567–576.
- 361 Eastwood, J. W., Hockney, R. W., and Lawrence, D. (1980) P3M3DP—The three-dimensional periodic particle-
362 particle/particle-mesh program, *Computer Physics Communications*, 19, 215–261.
- 363 Farkas, D. (2000) Atomistic theory and computer simulation of grain boundary structure and diffusion, *Journal of Physics:*
364 *Condensed Matter*, 12, R497.
- 365 Fei, H., Koizumi, S., Sakamoto, N., Hashiguchi, M., Yurimoto, H., Marquardt, K., Miyajima, N., Yamazaki, D., and Katsura,
366 T. (2016) New constraints on upper mantle creep mechanism inferred from silicon grain-boundary diffusion rates, *Earth and*
367 *Planetary Science Letters*, 433, 350–359.
- 368 Furstoss, J., Petit, C., Tommasi, A., Ganino, C., Muñoz, D. P., and Bernacki, M. (2021) On the role of solute drag in reconciling
369 laboratory and natural constraints on olivine grain growth kinetics, *Geophysical Journal International*, 224, 1360–1370.
- 370 Ghosh, D. B. and Karki, B. B. (2014) First principles simulations of the stability and structure of grain boundaries in Mg₂
371 SiO₄ forsterite, *Physics and Chemistry of Minerals*, 41, 163–171.
- 372 Gui-Jin, W. and Vitek, V. (1986) Relationships between grain boundary structure and energy, *Acta Metallurgica*, 34, 951–960.
- 373 Hafner, J. (2008) Ab-initio simulations of materials using VASP: Density-functional theory and beyond, *Journal of computa-*
374 *tional chemistry*, 29, 2044–2078.
- 375 Han, J., Vitek, V., and Srolovitz, D. J. (2016) Grain-boundary metastability and its statistical properties, *Acta Materialia*,
376 104, 259–273.
- 377 Han, J., Vitek, V., and Srolovitz, D. J. (2017) The grain-boundary structural unit model redux, *Acta Materialia*, 133, 186–199.

- 378 Heinemann, S., Wirth, R., Gottschalk, M., and Dresen, G. (2005) Synthetic [100] tilt grain boundaries in forsterite: 9.9 to 21.5,
379 Physics and chemistry of minerals, 32, 229–240.
- 380 Henkelman, G., Arnaldsson, A., and Jónsson, H. (2006) A fast and robust algorithm for Bader decomposition of charge density,
381 Computational Materials Science, 36, 354–360.
- 382 Hirel, P. (2015) AtomsK: A tool for manipulating and converting atomic data files, Computer Physics Communications, 197,
383 212–219.
- 384 Hirel, P., Moladje, G. F. B., Carrez, P., and Cordier, P. (2019) Systematic theoretical study of [001] symmetric tilt grain
385 boundaries in MgO from 0 to 120 GPa, Physics and Chemistry of Minerals, 46, 37–49.
- 386 Hirel, P., Furstoss, J., and Carrez, P. (2021) A critical assessment of interatomic potentials for modelling lattice defects in
387 forsterite Mg₂SiO₄ from 0 to 12 GPa, Physics and Chemistry of Minerals, 48, 1–16.
- 388 Hirth, G. and Kohlstedt, D. L. (1995) Experimental constraints on the dynamics of the partially molten upper mantle: Deformation
389 in the diffusion creep regime, Journal of Geophysical Research: Solid Earth, 100, 1981–2001.
- 390 Jacobsen, S. D., Demouchy, S., Frost, D. J., Ballaran, T. B., and Kung, J. (2005) A systematic study of OH in hydrous
391 wadsleyite from polarized FTIR spectroscopy and single-crystal X-ray diffraction: Oxygen sites for hydrogen storage in
392 Earth's interior, American Mineralogist, 90, 61–70.
- 393 Kim, M., Duscher, G., Browning, N. D., Sohlberg, K., Pantelides, S. T., and Pennycook, S. J. (2001) Nonstoichiometry and
394 the electrical activity of grain boundaries in SrTiO₃, Physical review letters, 86, 4056.
- 395 Kresse, G. and Joubert, D. (1999) From ultrasoft pseudopotentials to the projector augmented-wave method, Physical review
396 b, 59, 1758.
- 397 Mantisi, B., Sator, N., and Guillot, B. (2017) Structure and transport at grain boundaries in polycrystalline olivine: An
398 atomic-scale perspective, Geochimica et Cosmochimica Acta, 219, 160–176.
- 399 Marquardt, K. and Faul, U. H. (2018) The structure and composition of olivine grain boundaries: 40 years of studies, status
400 and current developments, Physics and Chemistry of Minerals, 45, 139–172.
- 401 Marquardt, K., Rohrer, G. S., Morales, L., Rybacki, E., Marquardt, H., and Lin, B. (2015) The most frequent interfaces in
402 olivine aggregates: the GBCD and its importance for grain boundary related processes, Contributions to Mineralogy and
403 Petrology, 170, 1–17.
- 404 Maruyama, G. and Hiraga, T. (2017a) Grain-to multiple-grain-scale deformation processes during diffusion creep of forsterite+
405 diopside aggregate: 1. Direct observations, Journal of Geophysical Research: Solid Earth, 122, 5890–5915.
- 406 Maruyama, G. and Hiraga, T. (2017b) Grain-to multiple-grain-scale deformation processes during diffusion creep of forsterite+
407 diopside aggregate: 2. Grain boundary sliding-induced grain rotation and its role in crystallographic preferred orientation
408 in rocks, Journal of Geophysical Research: Solid Earth, 122, 5916–5934.
- 409 McGibbon, M., Browning, N., Chisholm, M., McGibbon, A., Pennycook, S., Ravikumar, V., and Dravid, V. (1994) Direct
410 determination of grain boundary atomic structure in SrTiO₃, Science, 266, 102–104.
- 411 Mishin, Y. and Farkas, D. (1998) Atomistic simulation of [001] symmetrical tilt grain boundaries in NiAl, Philosophical Magazine
412 A, 78, 29–56.
- 413 Monkhorst, H. J. and Pack, J. D. (1976) Special points for Brillouin-zone integrations, Physical review B, 13, 5188.
- 414 Oh, Y. and Vitek, V. (1986) Structural multiplicity of $\Sigma=5$ (001) twist boundaries and interpretation of X-ray diffraction from
415 these boundaries, Acta Metallurgica, 34, 1941–1953.
- 416 Pedone, A., Malavasi, G., Menziani, M. C., Cormack, A. N., and Segre, U. (2006) A new self-consistent empirical interatomic

- 417 potential model for oxides, silicates, and silica-based glasses, *The Journal of Physical Chemistry B*, 110, 11 780–11 795.
- 418 Perdew, J. P. and Wang, Y. (1992) Accurate and simple analytic representation of the electron-gas correlation energy, *Physical*
419 *review B*, 45, 13 244.
- 420 Perdew, J. P., Burke, K., and Ernzerhof, M. (1996) Generalized gradient approximation made simple, *Physical review letters*,
421 77, 3865.
- 422 Plimpton, S. (1995) Fast parallel algorithms for short-range molecular dynamics, *Journal of computational physics*, 117, 1–19.
- 423 Read, W. T. and Shockley, W. (1950) Dislocation models of crystal grain boundaries, *Physical review*, 78, 275.
- 424 Rittner, J. and Seidman, D. N. (1996) $\langle 110 \rangle$ symmetric tilt grain-boundary structures in fcc metals with low stacking-fault
425 energies, *Physical Review B*, 54, 6999.
- 426 Smyth, J. R. (1994) A crystallographic model for hydrous wadsleyite (β -Mg₂SiO₄): an ocean in the Earth's interior?, *American*
427 *Mineralogist*, 79, 1021–1024.
- 428 Sun, X.-Y., Cordier, P., Taupin, V., Fressegeas, C., and Jahn, S. (2016) Continuous description of a grain boundary in
429 forsterite from atomic scale simulations: the role of disclinations, *Philosophical Magazine*, 96, 1757–1772.
- 430 Tang, W., Sanville, E., and Henkelman, G. (2009) A grid-based Bader analysis algorithm without lattice bias, *Journal of*
431 *Physics: Condensed Matter*, 21, 084 204.
- 432 Tschopp, M. A., Solanki, K., Gao, F., Sun, X., Khaleel, M. A., and Horstemeyer, M. (2012) Probing grain boundary sink
433 strength at the nanoscale: Energetics and length scales of vacancy and interstitial absorption by grain boundaries in α -Fe,
434 *Physical Review B*, 85, 064 108.
- 435 Uberuaga, B. P., Vernon, L. J., Martinez, E., and Voter, A. F. (2015) The relationship between grain boundary structure,
436 defect mobility and grain boundary sink efficiency, *Scientific reports*, 5, 1–9.
- 437 Vitek, V. (1968) Intrinsic stacking faults in body-centred cubic crystals, *Philosophical Magazine*, 18, 773–786.
- 438 Yang, H., Lee, H., Sarahan, M., Sato, Y., Chi, M., Moeck, P., Ikuhara, Y., and Browning, N. D. (2013) Quantifying
439 stoichiometry-induced variations in structure and energy of a SrTiO₃ symmetric $\Sigma 13 \{510\} / \langle 100 \rangle$ grain boundary, *Philo-*
440 *sophical Magazine*, 93, 1219–1229.
- 441 Yurimoto, H., Morioka, M., and Nagasawa, H. (1992) Oxygen self-diffusion along high diffusivity paths in forsterite, *Geochemical*
442 *Journal*, 26, 181–188.

443 **List of Figures**

444 1 Typical oriented unit cells of forsterite used to construct the STGBs. Basic crystallographic
 445 directions [010] and [001] are indicated. Crystals are rotated around the [100] axis normal to
 446 the figure. Insets show cells of forsterite terminated by (1c) Si planes, and (1b) Mg planes
 447 (see text). 18

448 2 Summary of the methodology used to compute the GB energy landscape, from the relaxation
 449 of the reference configuration (left) to the sampling of the surface (right). The constraints on
 450 relaxation in the different layers are: (1) Mg and Si ions fixed in the (X,Y) plane and O free
 451 to move in all directions; (2) all ions fixed in all directions; and (3) all ions free to relax in all
 452 directions. 19

453 3 Energy landscapes for the $60.8^\circ//[100](011)$ STGB in forsterite, computed for its edge-to-
 454 edge (3a) and tip-to-tip (3b) configurations (see Fig.2), following the methodology presented
 455 in section 2.3. 20

456 4 Atomic structures and density profiles of fully relaxed low energy GBs. Labels refer to those
 457 in Fig.3, for edge-to-edge (E1,E2,E3) and tip-to-tip (T1,T2,T3) GBs. GB energies and excess
 458 volumes come from MD calculations. 21

459 5 Results of Bader analysis performed on the E2 stoichiometric GB complexion (see Fig.4b).
 460 Figure (5a) : isosurfaces of charge density (level at 0.05e) belonging to different O ions,
 461 figure (5b) : O charge distributions in a perfect crystal environment (blue) and in the system
 462 containing the GB (orange). 22

463 6 MgO vacancy pair segregation energy in the vicinity of the E1 complexion (see Fig.4a). 23

464 7 Atomic structure and density profile of the non stoichiometric (with vacancy pairs) GBs with
 465 the lowest energy differences for each low energy parent complexions presented in figure 4.
 466 Labels refer to those in Fig.3. 24

467 8 Results of Bader analysis performed on the non-stoichiometric E2 GB complexion (see Fig.7b).
 468 Figure (8a) : isosurfaces of charge density (level at 0.05e) belonging to different O ions.
 469 Figure (8b) : O charge distributions in a perfect crystal environment (blue) and in the system
 470 containing the GB (orange), the red arrow points the O ions highlighted in red in the sketch
 471 zooming on the interface, the blue arrow points the O ions highlighted in dark blue in the
 472 sketch and the blue circle points the O ions highlighted in light blue in the sketch. 25

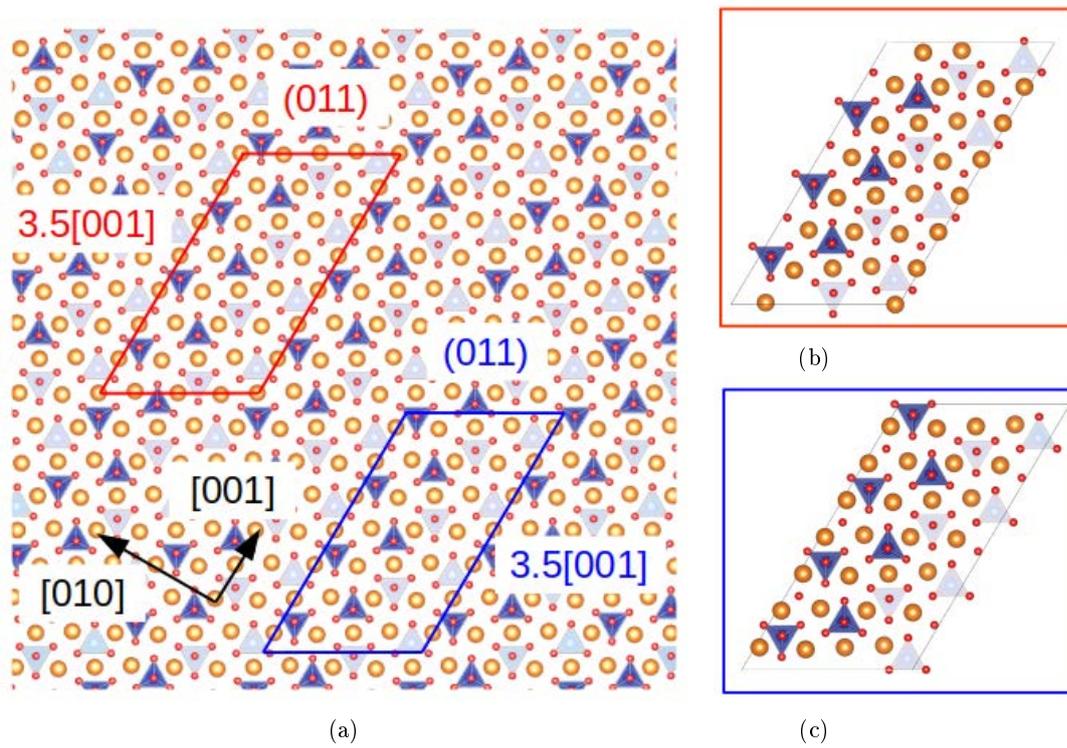


Figure 1: Typical oriented unit cells of forsterite used to construct the STGBs. Basic crystallographic directions [010] and [001] are indicated. Crystals are rotated around the [100] axis normal to the figure. Insets show cells of forsterite terminated by (1c) Si planes, and (1b) Mg planes (see text).

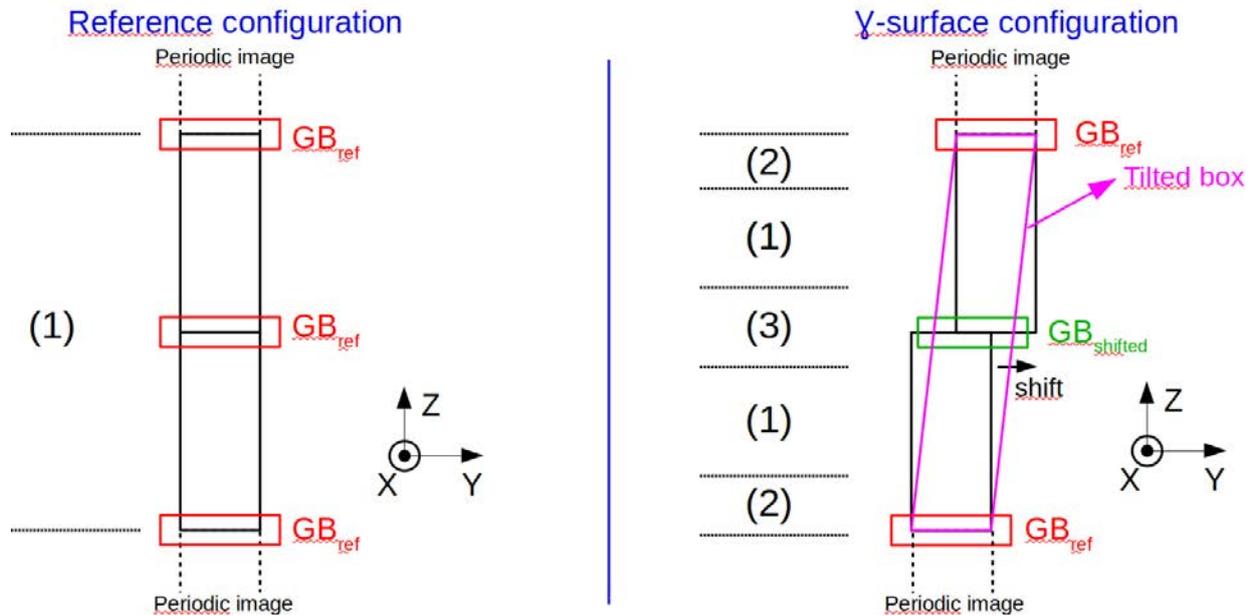


Figure 2: Summary of the methodology used to compute the GB energy landscape, from the relaxation of the reference configuration (left) to the sampling of the surface (right). The constraints on relaxation in the different layers are: (1) Mg and Si ions fixed in the (X,Y) plane and O free to move in all directions; (2) all ions fixed in all directions; and (3) all ions free to relax in all directions.

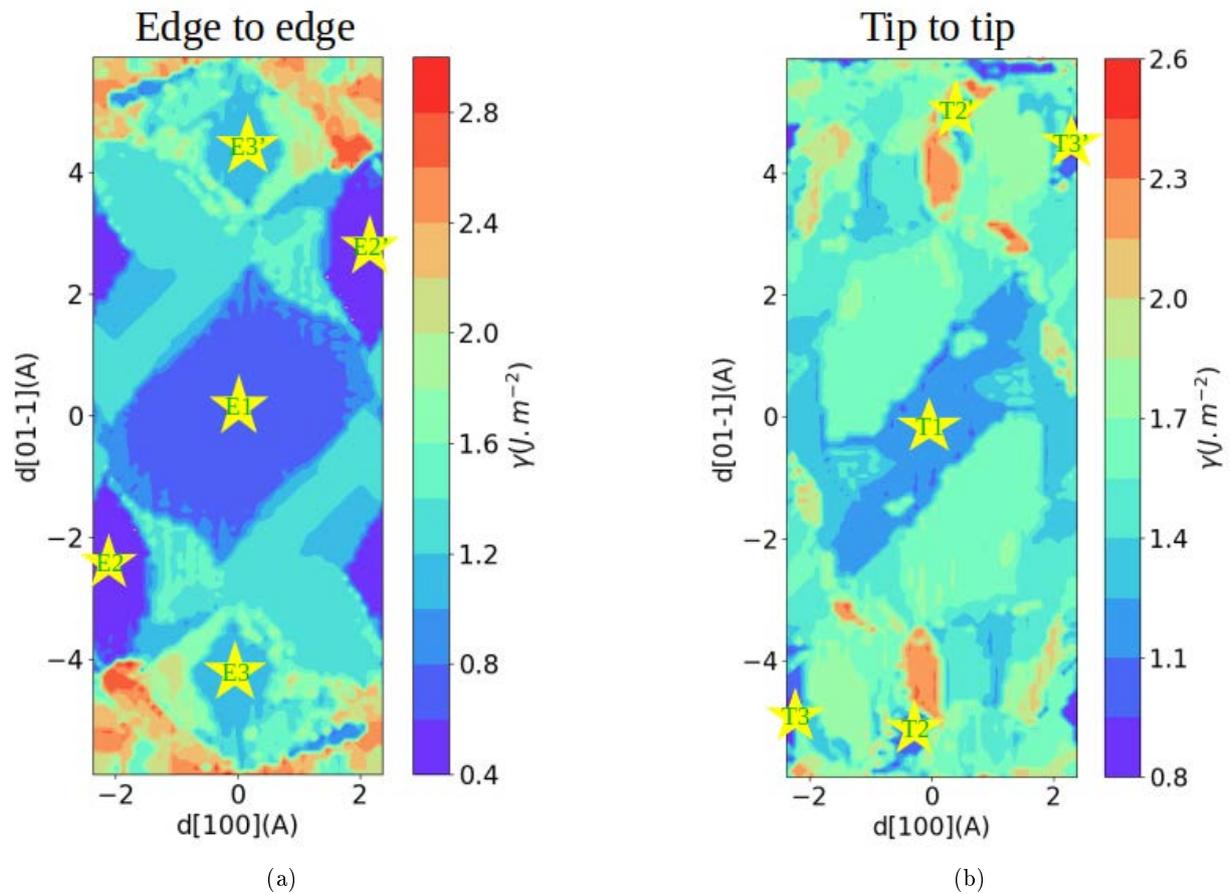


Figure 3: Energy landscapes for the $60.8^\circ//[100](011)$ STGB in forsterite, computed for its edge-to-edge (3a) and tip-to-tip (3b) configurations (see Fig.2), following the methodology presented in section 2.3.

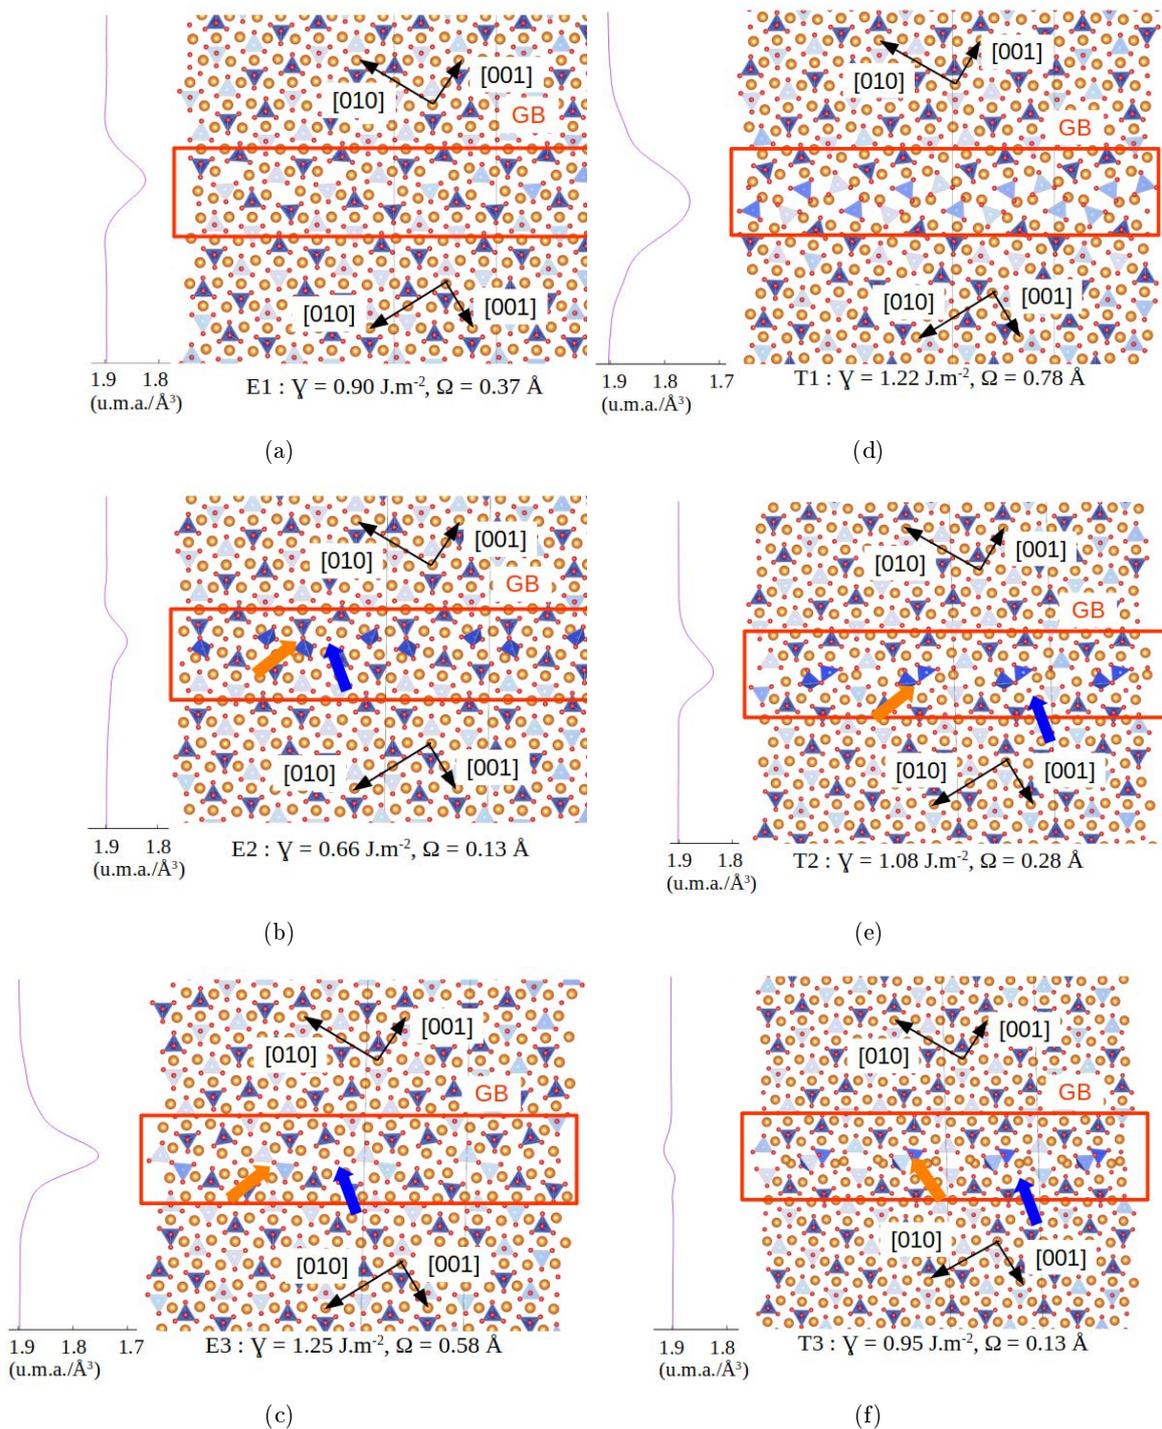


Figure 4: Atomic structures and density profiles of fully relaxed low energy GBs. Labels refer to those in Fig.3, for edge-to-edge (E1,E2,E3) and tip-to-tip (T1,T2,T3) GBs. GB energies and excess volumes come from MD calculations.

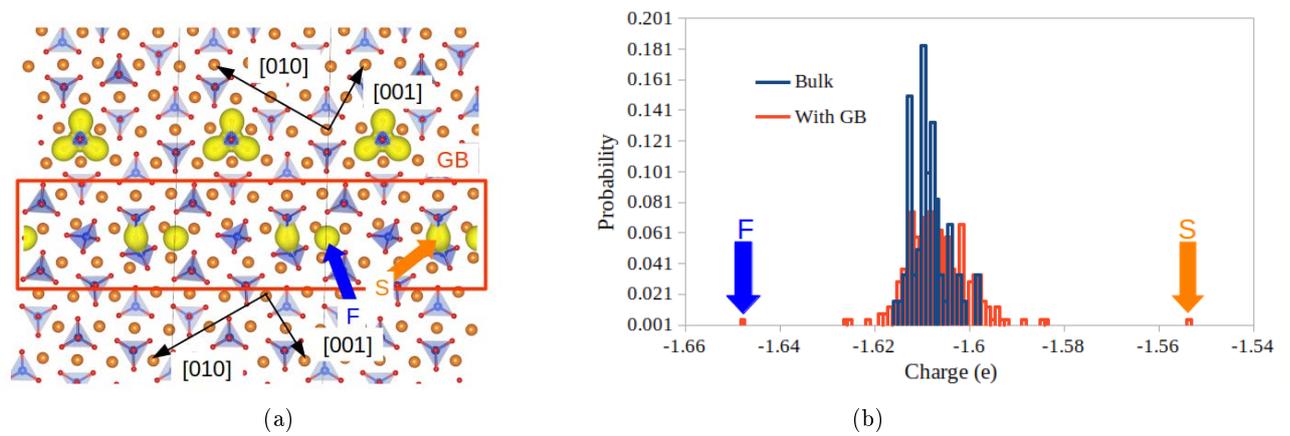


Figure 5: Results of Bader analysis performed on the E2 stoichiometric GB complex (see Fig.4b). Figure (5a) : isosurfaces of charge density (level at 0.05e) belonging to different O ions, figure (5b) : O charge distributions in a perfect crystal environment (blue) and in the system containing the GB (orange).

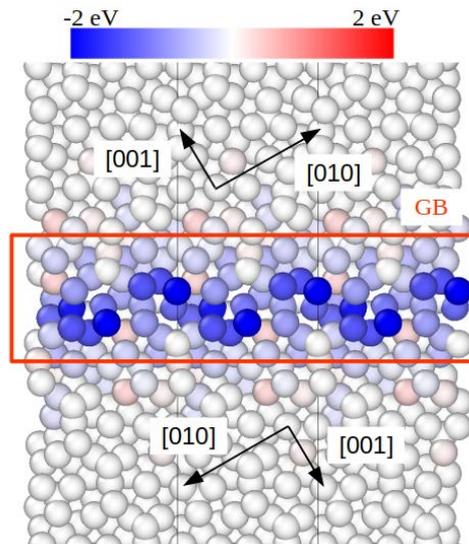


Figure 6: MgO vacancy pair segregation energy in the vicinity of the E1 complex (see Fig.4a).

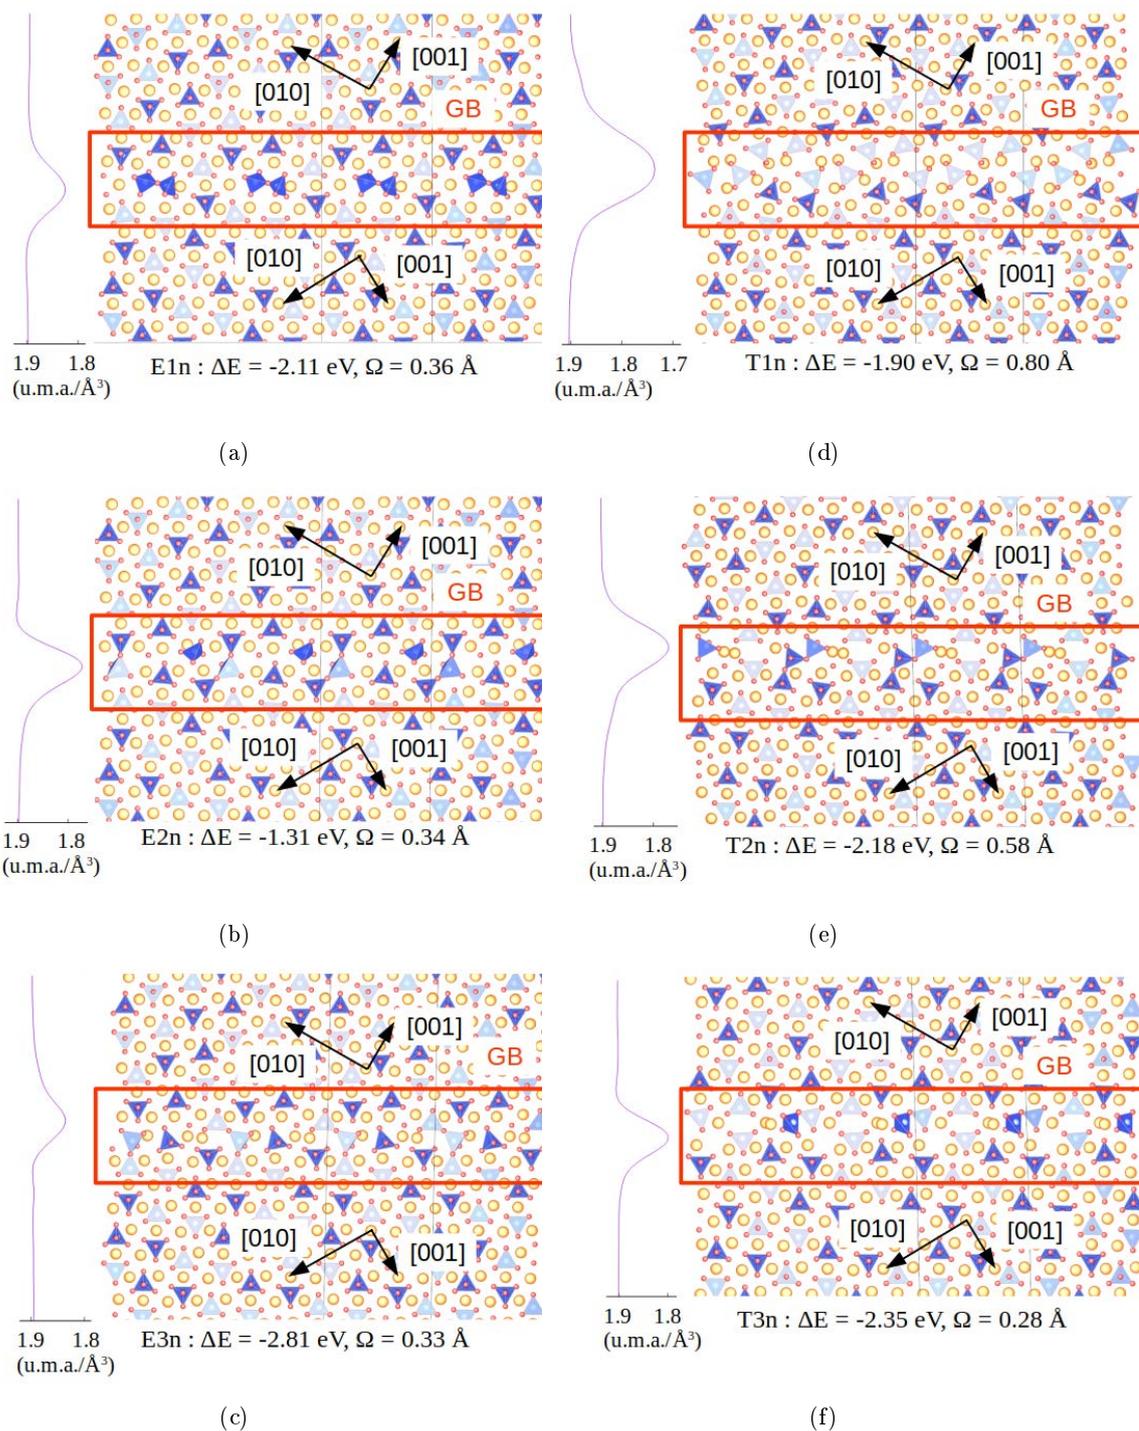


Figure 7: Atomic structure and density profile of the non stoichiometric (with vacancy pairs) GBs with the lowest energy differences for each low energy parent complexes presented in figure 4. Labels refer to those in Fig.3.

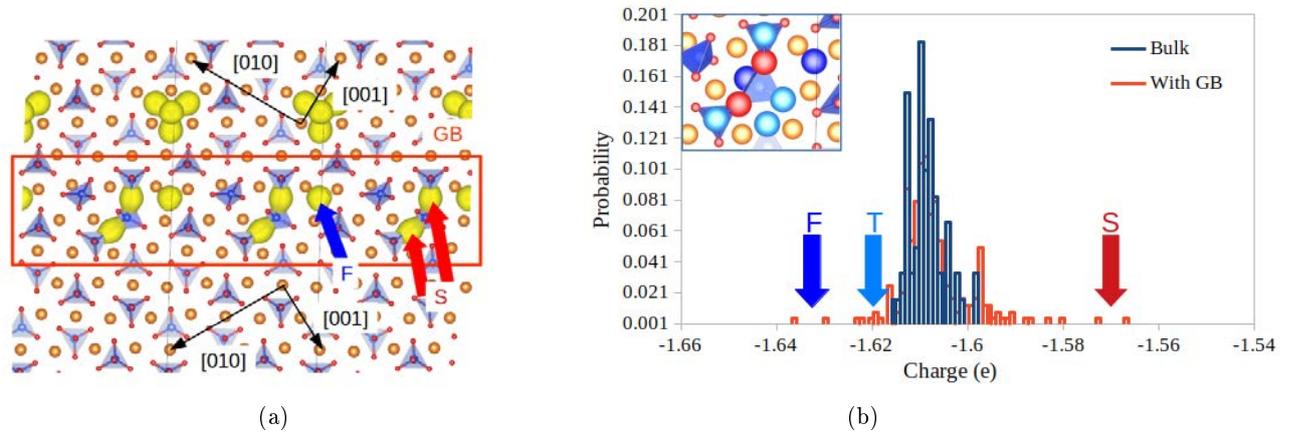


Figure 8: Results of Bader analysis performed on the non-stoichiometric E2 GB complex (see Fig.7b). Figure (8a) : isosurfaces of charge density (level at 0.05e) belonging to different O ions. Figure (8b) : O charge distributions in a perfect crystal environment (blue) and in the system containing the GB (orange), the red arrow points the O ions highlighted in red in the sketch zooming on the interface, the blue arrow points the O ions highlighted in dark blue in the sketch and the blue circle points the O ions highlighted in light blue in the sketch.